

ORIGINAL RESEARCH

Medicine Science 2019;8(3):541-4

**Green synthesized silver nanoparticles:
Morphology and antibacterial contact effects****Erdi Bilgic, Sinem Gurkan Aydin, Arzu Ozgen, Mustafa Nizamlioglu***Istanbul Gelisim University, Vocational School of Health Sciences, Department of Medical Services and Techniques, Istanbul, Turkey*

Received 06 December 2018; Accepted 25 February 2019

Available online 22.02.2019 with doi:10.5455/medscience.2018.07.8996

*Copyright © 2019 by authors and Medicine Science Publishing Inc.***Abstract**

In the study in which the green synthesis method was preferred, silver nanoparticles (Ag NP's), which preferred fig (*Ficus carica*) leaf extracts as a reducing agent, were obtained from their saline solutions. The morphological characteristics of the obtained Ag NPs were studied and antibacterial effects on 8 different bacteria (*K. pneumonia*, *E. coli*, *P. mirabilis*, *Shigella*, *A. baumannii*, *S. aureus*, *S. aureus*, *S. epidermidis*) were investigated. Transmission Electron Microscopy (TEM) and UV-Vis spectrophotometer determined morphology and formation of nanoparticles, respectively. The UV-vis absorbance spectra of AgNP exhibit increasing surface plasmon peaks with time of 446 nm. Nanoparticle sizes are at an average value of 13 nm in the 7-33 nm range. The antibacterial effects of Ag NPs vary from bacterial to bacterial and depending on the applied dose and show a contact effect. Positive results were obtained against both gram-positive and negative bacteria and the results were shared.

Keywords: Fig, *Ficus carica*, UV-Vis spectrophotometer, bacteria, silver nanoparticles**Introduction**

The bioactivities and uses of nano-sized metal particles are the research areas for increased interest [1]. Nano size metal particles exhibit extraordinary physical, chemical and biological properties due to their wide surface area and high reactivity comparison. The optical properties of Ag NP's according to their size, structure and chemical properties have been studied in detail [2,3]. In addition, Ag NP's have great interest in the use of silver as a special class of biocidal agents due to the extraordinary antibacterial properties [4,5]. For instance, sore wraps including Silver materials that are sprayed monocrystalline are used in clinical practice to prevent bacterial infection of burn wounds today [4]. Similarly, there are numerous Silver composite materials containing Ag NP's as an active antibacterial component [6-8].

In recent years, researchers in the field of nanotechnology have discovered that metal nanoparticles have all the undisclosed benefits. They are typically prepared from noble metals, that is, silver (Ag), gold (Au), Platinum (Pt), Copper (Cu) and Iron (Fe). Ag

NP's being most exploited [9]. They obtain applications in various fields such as medicine, electronics, energy saving, environment, textile, cosmetics, and so forth. Due to their applicability in such wide sectors, their demand is increasing at an overwhelming rate. The increased request has consequently resulted in increased production. Researchers are continuously developing newer methods for synthesis of highly monodisperse Ag NP's which are efficient in terms of synthesis rate as well as energy usage [10].

Traditionally, nanomaterials were synthesized using chemical or physical methods including left process, sol-gel, chemical sedimentation, hydrothermal method, pyrolysis and chemical vapour deposition [11]. Some of these methods provide easy control over the size of the crystal by restoring the reaction environment. The problem still occurs with the overall stability of the product, but it uses these methods in single-dispersion nanositm [12]. Moreover, most traditional techniques were found to be capital intensive and inefficient in the use of materials and energy [13].

Biological methods have emerged as an alternative to traditional methods in order to synthesize nanoparticles (NP's). Synthesis of inorganic particles by biological systems ensures that nanoparticles are environmentally friendly and biologically more compatible

***Corresponding Author:** Erdi Bilgic, Istanbul Gelisim University, Vocational School of Health Sciences, Department of Medical Services and Techniques, Istanbul, Turkey, E-mail: erbilgic@gelisim.edu.tr

[14]. Additionally, the procedure is cost effective too [10]. A lot of bacterial as well as fungal species were used for Ag NP's synthesis [15]. But most of them was reported to amass Ag NP's intracellularly. Intracellular synthesis always takes longer reaction times and moreover needs subsequent extraction and recovery steps. In contrast, plant extract mediated synthesis always takes place extracellularly, and the reaction times was stated to be very short compared to that of bacterial synthesis. Most importantly, the method be able to suitably scaled up for large scale synthesis of NP's.

A lot of plants such as Turmeric [16], [16], *Madhuca longifolia* [17], Lemongrass [18], Aloe vera [19], *Emblica officinalis* [20], *Tridax procumbens*, *Jatropha curcas*, *Solanum melongena*, *Datura metel*, *Citrus aurantium* [21] and many weeds [10] were shown the potential of lessening silver nitrate (AgNO_3) to give formation of silver nanoparticles.

In this study, green synthesis method was preferred and Ag NP's were obtained from AgNO_3 solutions using fig leaf extracts. Morphological characteristics of the obtained nanoparticles and their antibacterial effects on eight different bacterial cultures were investigated.

Material and Methods

AgNPs synthesis

1.00 gr fresh shaded dried figs (*Ficus Carica*) leaves were milled and mixed on a magnetic stirrer in 100 ml distilled water for 30 minutes. The resulting solution was passed through filter paper and then the fig extracts were obtained. The fig extracts were mixed at a ratio of 1:1 with 2mM AgNO_3 dissolved in distilled water. The mixtures were allowed to stand at room conditions for the synthesis of colloidal Ag NP's.

Characterization of Ag NPs

UV-vis absorbance spectrums of the synthesis colloidal Ag NP's were recorded in the wavelength range of 200-800 nm using Hitachi U-3900H double-beam spectrophotometer operating at a resolution of 1 nm. On the spectra, the fig extract diluted at a ratio of 1-1 with distilled water was taken as the reference solution, and the extract- AgNO_3 mixtures were examined in the presence of this reference solution. Quartz cuvettes were used in the spectrophotometer. The formation kinetics of Ag NP's were determined by absorbance spectra taken at periodic intervals of 20 minutes. Morphological characteristics of the Ag NP's were determined by ZEIS-LEO 906E brand-model Transmission Electron Microscopy (TEM).

Antibacterial activity

The antibacterial activity of the synthesized Ag NP's was assayed in Gram (-) bacteria (*Klebsiella pneumonia* ATCC 700603, *Escherichia coli* ATCC 25922, *Proteus mirabilis* ATCC 27853, *Shigella*, *Acinetobacter baumannii* ATCC BAA 747) and Gram (+) bacteria (*Staphylococcus aureus* ATCC 29213, *Staphylococcus aureus* ATCC 95923, *Staphylococcus epidermidis* ATCC 12228) by disc diffusion method on solid media. All the strains were obtained from Acibadem University Medical Microbiology Laboratory. The bacterial strains were grown for 16 hours at 37 °C in Nutrient Agar (NA). The densities of bacterial suspensions were adjusted to 0,5 McFarland turbidity standard (1,5 x 10⁸

CFU/mL) by diluted 1:100 with Nutrient Broth. Subsequently, 100 µl of bacteria cells were spread onto the NA Petri dishes using sterile spreader. Afterwards, sterile Whatman filter papers (6-mm-diameters) were placed over the medium using sterile forceps and were impregnated with 10, 30, 50, 70, 100 µl of Ag NP's. *Ficus carica* leaf extract was used as a negative control and Cefoperazone 75 mcg/disc and Doksisiklin 30 mcg/disc were used as positive control. The plates were incubated for 24 h at 37 °C. The growth inhibition zones of each disc were measured in millimeters. All experiments were duplicated.

Results

As soon as, Fig extract was mixed in aqueous solution of silver ion complex, the reduction of pure Ag^+ ions to Ag^0 was monitored by measuring UV-vis spectrum of the reaction media at regular intervals. UV-vis spectra were recorded as function of reaction time. The increase in peak intensities is related to the size of the nanoparticles as they are related to nucleation. Figure 1, nanoparticle sizes formed at the end of 40 minutes and nanoparticle sizes formed at the end of 100 minutes will be different from each other as can be seen from the peak intensities. As is known, nanoparticle sizes directly affect the antibacterial effects of Ag NP's.

Table 1 shows the particle sizes and shapes of Ag NP's obtained from different plant extracts. According to this table, which contains literature data, almost all of the nanoparticles have spherical shape and their dimensions vary from 4 to 150 nm. This change in particle size can be seen to be influenced by plants used as reducing agents. In this study, it was observed that the size distributions of the Ag NP's synthesized from the fig plant varied between 7 and 33 nm and the average 13 nm shapes were circular in accordance with the literature in Figure 2.

Table1. Dimensions and shapes of Ag NP's obtained by green synthesis method.

Reducing agent	Particles size (nm)	Particles Shape	SPR peak	Ref.
Turmeric	18 ±0.5	Spherical	432	16
<i>Madhuca longifolia</i>	30-50	Spherical, oval	436	17
Grass waste	15	spherical-oblate	430-450	18
<i>Carica papaya</i>	7-25	Spherical	429	19
Green Tea	3.9 ±1.6	Spherical	410	26
<i>Abutilon indicum</i>	50-100	Spherical	420	27
<i>Rheum turkestanicum</i>	26	Spherical	441	28
<i>Bauhinia purpurea</i>	12-50	Spherical	435	29

UV-vis absorbance spectra of Ag NP's obtained by green synthesis are given the table 1. According to these spectra, the values of the SPR peaks related to the formation of Ag nanoparticles range from 408 to 450 nm. In this study, it was observed that the UV-vis absorbance spectra of mixtures exhibited increasing SPR peaks at 446 nm, similar to the literature.

The antibacterial activity of mixtures that contain Ag NP's and *Ficus carica* leaf extract tested against the human pathogen Gram (-) bacteria (*Klebsiella pneumonia* ATCC 700603, *Escherichia coli* ATCC 25922, *Proteus mirabilis* ATCC 27853, *Shigella*,

Acinetobacter baumannii ATCC BAA 747) and Gram (+) bacteria (*Staphylococcus aureus* ATCC 29213, *Staphylococcus aureus* ATCC 95923, *Staphylococcus epidermidis* ATCC 12228) at various concentration. The results were given in Table 2.

According to results, the synthesized Ag NP's and *Ficus carica* leaf extract mixture inhibited the bacterial growth both Gram (+) and Gram (-) bacteria strains, especially in *Klebsiella pneumonia* ATCC 700603. Inhibition zone changes according to the bacterial strain, for example antibacterial activity starts at 70 μ L for *Proteus mirabilis*.

The morphology of silver nanoparticles synthesized using fig leaves and the antibacterial effect on G (+) and G (-) bacterial strains were investigated. As a result, the minimum dose amounts that the antibacterial effect changed with respect to the bacteria and which should be used were determined. Dose data of the study with a concentration of 1 mm was obtained. It is suggested

to obtain new bacteria in different bacterial strains at different concentrations.

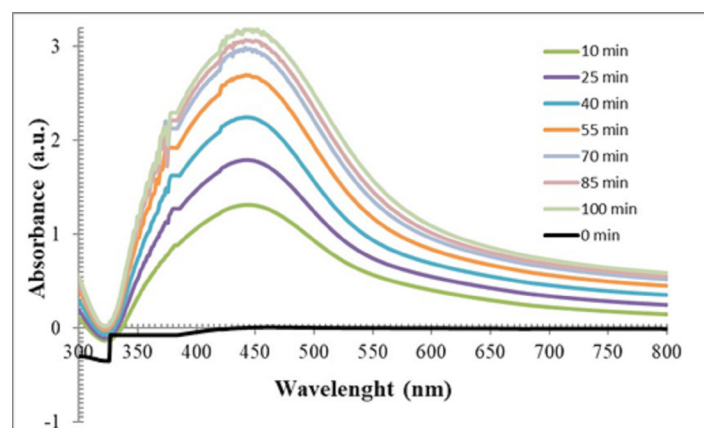


Figure 1. The UV-vis absorbance spectra of the fig extract-AgNO₃ mixture as a function of time.

Table 2. The inhibition zone in diameter (mm) formed around the discs impregnated with mixtures in various volume

Bacteria Species	Plant extract	10 μ L/disc	30 μ L/disc	50 μ L/disc	70 μ L/disc	100 μ L/disc	Doxycycline 30 mcg/disc	Cefoperazone 75 mcg/disc
<i>K. pneumonia</i> ATCC 700603	-	-	11	disc	18	22.5	20	
<i>E. coli</i> ATCC 25922	-	9	11.5	16.5	13.5	15.5	23	
<i>P. mirabilis</i> ATCC 27853	-	-	-	12.5	12	15	24	
<i>Shigella</i>	-	-	-	-	12.5	14.5	17	28
<i>A. baumannii</i> ATCC BAA	-	0	10	9	14	18	23	
<i>S. aureus</i> ATCC 29213	-	7.5	9.5	13	13	13.5	29	25
<i>S. aureus</i> ATCC 95923	-	-	11	11	14	14.5	30	24
<i>S. epidermidis</i> ATCC 12228	-	-	7	12	13	16.5	28	23

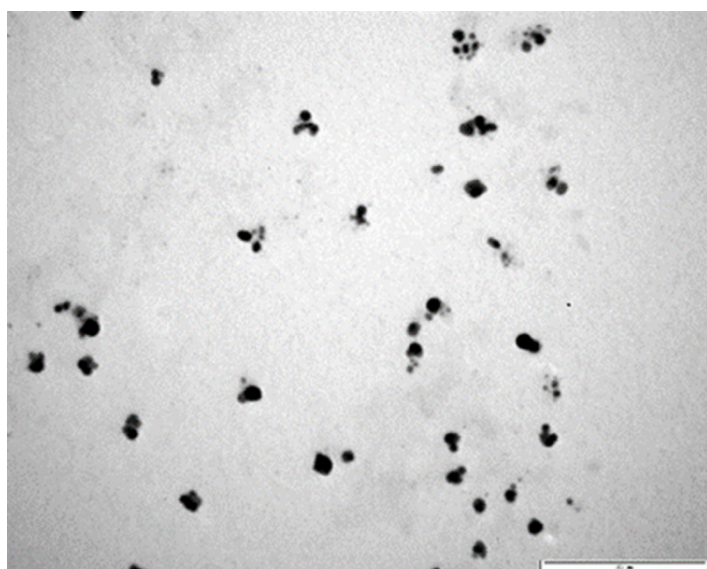


Figure 2. Transmission Electron Microscopy (TEM) imaging of Ag NP's.

Discussion

In many studies, the antibacterial effects of nanoparticles were emphasized, and the effects of nanoparticle solutions on different bacteria were investigated (Table 1). In these studies, it

is emphasized that the inhibition area is expanding. In some of these studies, it was suggested that the interaction of the bacteria with the nanoparticle solution increased due to the increase of the volume. The Ag-NPs are capable of inhibiting the bacterial growth due to their small size and large surface area which provide sufficient contact with the bacteria [30]. Since this volumetric increase will not directly increase the nanoparticle concentration on the surface of the unit, it can be said that the antibacterial effect will not increase due to the solution volume and the expansion of the field may cause antibacterial effect due to the increase in contact with bacteria due to the fluidity of the solution. As the volume of the nanoparticles increases, the area it covers on the petri increases and this expands the inhibition area. Ag NP's are positively charged and can easily bind and interact with the negatively charged bacterial cell wall. Nanoparticles that move to the cytoplasm prevent expression of essential proteins for cell and cause cell death [22-25]. As a result, the contact effect of Ag NP's dependent on the plant which is used can be mentioned.

Competing interests

The authors declare that they have no competing interest.

Financial Disclosure

All authors declare no financial support.

Ethical approval

Consent of ethics was approved by the local ethics committee.

Erdi Bilgic ORCID: 0000-0002-2892-274X

Sinem Gurkan Aydin ORCID: 0000-0002-5146-8936

Arzu Ozgen ORCID: 0000-0003-2104-6019

Mustafa Nizamlioglu ORCID: 0000-0002-2104-784X

References

1. Sonnichsen C, Reinhard BM, Liphardt J, Alivisatos. A molecular ruler based on plasmon coupling of single gold and silver nanoparticles. *AP. Nat Biotechnol.* 2005;23:41-745.
2. Jin R, Cao Y, Mirkin CA, et al. Photoinduced conversion of silver nanospheres to nanoprisms. *Sci.* 2001;294:1901-3.
3. Henglein A. Physicochemical properties of small metal particles in solution: "microelectrode" reactions, chemisorption, composite metal particles, and the atom-to-metal transition. *J Phys Chem.* 1993;97:5457-71.
4. Olson ME, Wright JB, Lam K, et al. Healing of porcine donor sites covered with silver coated dressings. *Eur J Surg.* 2000;166:486-9.
5. Sun RW, Chen R, Chung NP, et al. Silver nanoparticles fabricated in Hepes buffer exhibit cytoprotective activities toward HIV-1 infected cells. *Chem Commun.* 2005;40:5059-61.
6. Aymonier C, Schlotterbeck U, Antonietti L, et al. Hybrids of silver nanoparticles with amphiphilic hyperbranched macromolecules exhibiting antimicrobial properties. *Chem Commun.* 2002;24:3018-9.
7. Podsiadlo P, Paternel S, Rouillard JM, et al. Layer-by-layer assembly of nacre-like nanostructured composites with antimicrobial properties. *Langmuir.* 2005;21:11915-21.
8. Tian J, Wong KK, Ho CM, et al. Topical delivery of silver nanoparticles promotes wound healing. *Chem Med Chem.* 2007;2:129-36.
9. Roy N, Barik A. Green synthesis of silver nanoparticles from the unexploited weed resources. *Int J Nanotechnol.* 2010;4:95.
10. Charusheela R, Tapan C, Bijaya S, et al. Synthesis of silver nanoparticles from the aqueous extract of leaves of ocimum sanctum for enhanced antibacterial activity. *J chem.* 2013;278925:7.
11. Leela A, Vivekanandan M. Tapping the unexploited plant resources for the synthesis of silver nanoparticles. *Afr J Biotechnol.* 2008;17:3162-5.
12. Kowshik M, Deshmukh N, Vogel W, et al. Microbial synthesis of semiconductor CdS nanoparticles, their characterization, and their use in the fabrication of an ideal diode. *Biotechnol. Bioeng.* 2002;78:583-8.
13. Klaus Joerger T, Joerger R, Olsson E, et al. Bacteria as workers in the living factory: metal-accumulating bacteria and their potential for materials science. *Trends Biotechnol.* 2001;1:15-20.
14. Govindaraju K, Tamilselvan S, Kiruthiga V, et al. Biogenic silver nanoparticles by Solanum torvum and their promising antimicrobial activity. *J Biopesticides.* 2010;3:394-9.
15. Mandal D, Bolander ME, Mukhopadhyay D, et al. The use of microorganisms for the formation of metal nanoparticles and their application. *Appl Microbiol Biotechnol.* 2006;69:485-92.
16. Alsammarraie FK, Wang W, Zhou P, et al. Green synthesis of silver nanoparticles using turmeric extracts and investigation of their antibacterial activities. *Colloids and Surfaces B: Biointerfaces.* 2018;171:398-405.
17. Patil MP, Singh RD, Koli PB, et al. Antibacterial potential of silver nanoparticles synthesized using Madhuca longifolia flower extract as a green resource. *Microb Pathog.* 2018;121:184-9.
18. Khatami M, Sharifi I, Nobre MA, et al. Waste-grass-mediated green synthesis of silver nanoparticles and evaluation of their anticancer, antifungal and antibacterial activity. *Green Chemistry Letters and Reviews.* 2018;11:125-34.
19. Bindhu MR, Amala BM, Jeeva M. Green synthesis of silver nanoparticles and its antibacterial activity. 2017
20. Ankamwar B, Damle C, Ahmad A, et al. Biosynthesis of gold and silver nanoparticles using Emblica officinalis fruit extract, their phase transfer and transmetalation in an organic solution. *J Nanosci Nanotechnol.* 2005;5:1665-71.
21. Rajasekharreddy P, Rani PU, Sreedhar B. Qualitative assessment of silver and gold nanoparticle synthesis in various plants: a photobiological approach. *J. Nanopart Res.* 2010;12:1711-21.
22. Balalakshmi C, Gopinath K. Green synthesis of silver nanoparticles using Sphaeranthus indicus leaf extract and their antibacterial activity. *J Pharm Res Int.* 2017;4:679-682.
23. Gopinath K, Gowri S, Arumugam A. Phytosynthesis of silver nanoparticles using Pterocarpus santalinus leaf extract and their antibacterial properties. *J Nanostructure Chem.* 2013;3:68.
24. Gopinath K, Kumaraguru S, Bhakayaraj K, et al. Green synthesis of silver, gold and silver/gold bimetallic nanoparticles using the Gloriosa superba leaf extract and their antibacterial and antibiofilm activities. *Microb Pathog.* 2016;101:1-11.
25. Karthika V, Arumugam A, Gopinath K, et al. Phytosynthesis of silver nanoparticles using Pterocarpus santalinus leaf extract and their antibacterial properties. *J Photochem Photobiol B.* 2017;167:189-99.
26. Rolim WR, Pelegriño MT, de Araújo Lima B, et al. Green tea extract mediated biogenic synthesis of silver nanoparticles: Characterization, cytotoxicity evaluation and antibacterial activity. *Applied Surface Sci.* 2019;463:66-74.
27. Chandirika JU, Annadurai G. Biosynthesis and Characterization of Silver Nanoparticles Using Leaf Extract Abutilon indicum. *Global J Biotechnol Biochemistry.* 2018;13: 07-11.
28. Yazdi MET, Khara J, Sadeghnia HR, et al. Biosynthesis, characterization, and antibacterial activity of silver nanoparticles using Rheum turkestanicum shoots extract. *Rese Chemical Int.* 2018;442:1325-34.
29. Chinnappan S, Kandasamy S, Arumugam S, et al. Biomimetic synthesis of silver nanoparticles using flower extract of Bauhinia purpurea and its antibacterial activity against clinical pathogens. *Environ Sci Pollut Res Int.* 2018;25:963-9.
30. Kanmani P, Rhim JW. Physicochemical properties of gelatin/silver nanoparticle antimicrobial composite films. *Food Chemistry.* 2014;148:162-9.